



**CHALMERS**  
UNIVERSITY OF TECHNOLOGY

## **Engineering underdoped CuO<sub>2</sub> nanoribbons in nm-thick a -axis YBa<sub>2</sub>Cu<sub>3</sub> O<sub>7-δ</sub> films**

Downloaded from: <https://research.chalmers.se>, 2026-04-04 10:58 UTC

Citation for the original published paper (version of record):

Arpaia, R., Alcalde Herraiz, N., D'Alessio, A. et al (2024). Engineering underdoped CuO<sub>2</sub> nanoribbons in nm-thick a -axis YBa<sub>2</sub>Cu<sub>3</sub> O<sub>7-δ</sub> films. *Physical Review Materials*, 8(4).  
<http://dx.doi.org/10.1103/PhysRevMaterials.8.044803>

N.B. When citing this work, cite the original published paper.

Engineering underdoped CuO<sub>2</sub> nanoribbons in nm-thick *a*-axis YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> filmsRiccardo Arpaia <sup>1,\*</sup>, N ria Alcalde-Herraiz <sup>1</sup>, Andrea D'Alessio,<sup>1,2,†</sup> Evgeny Stepanov,<sup>1,3</sup> Eric Wahlberg <sup>1,4</sup>, Alexei Kalaboukhov <sup>1</sup>, Thilo Bauch <sup>1</sup> and Floriana Lombardi <sup>1,‡</sup><sup>1</sup>Quantum Device Physics Laboratory, Department of Microtechnology and Nanoscience, Chalmers University of Technology, SE-41296 G teborg, Sweden<sup>2</sup>Dipartimento di Fisica, Politecnico di Milano, piazza Leonardo da Vinci 32, I-20133 Milano, Italy<sup>3</sup>Shubnikov Institute of Crystallography of the Federal Scientific Research Centre "Crystallography and Photonics" of the Russian Academy of Sciences, Leninskiy prospekt 59, Moscow RU-119333, Russia<sup>4</sup>RISE Research Institutes of Sweden, Box 857, SE-50115 Bor s, Sweden

(Received 23 November 2023; revised 27 February 2024; accepted 1 April 2024; published 25 April 2024)

In underdoped cuprate high- $T_c$  superconductors, various local orders and symmetry-breaking states, in addition to superconductivity, reside in the CuO<sub>2</sub> planes. The confinement of the CuO<sub>2</sub> planes can therefore play a fundamental role in modifying the hierarchy between the various orders and their intertwining with superconductivity. Here we present the growth of *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> films, spanning the whole underdoped side of the phase diagram. In these samples, the CuO<sub>2</sub> planes are confined by the film thickness, effectively forming unit-cell-thick nanoribbons. The unidirectional confinement at the nanoscale enhances the in-plane anisotropy of the films. By x-ray diffraction and resistance vs temperature measurements, we have discovered the suppression of the orthorhombic-to-tetragonal transition at low dopings, and a very high anisotropy of the normal state resistance in the *b*-*c* plane, the latter being connected to a weak coupling between adjacent CuO<sub>2</sub> nanoribbons. These findings show that the samples we have grown represent a novel system, different from the bulk, where future experiments can possibly shed light on the rich and mysterious physics occurring within the CuO<sub>2</sub> planes.

DOI: [10.1103/PhysRevMaterials.8.044803](https://doi.org/10.1103/PhysRevMaterials.8.044803)

## I. INTRODUCTION

Cuprate high critical temperature superconductors (HTSs) represent a prominent example of compounds dominated by strong electron-electron correlations. Here all the relevant physics takes place in planes, where a single copper atom is at the center of a square of oxygen ligands. Despite this apparent simplicity, these materials host some of the most intricate quantum phases, dominated by strong interactions between spin, charge, and orbital degrees of freedom, which are controlled by the element atomic positions within the crystal lattice [1]. Unraveling such intricate ground state is a grand challenge: the large electron-electron repulsion and the consequent short-range antiferromagnetic correlations, within the low-dimensional CuO<sub>2</sub> planes [see orange surfaces in Fig. 1(a)], render HTS systems intrinsically different from standard metals, generally well understood in

terms of the Landau Fermi liquid paradigm. The resulting phase diagram, as a function of the doping and of the temperature, is very rich and complex, hosting many intertwined and/or competing local ordering phenomena breaking the rotational/translational symmetry [2,3]. Examples of these orders, all residing within the CuO<sub>2</sub> planes, are charge density waves (CDWs) [4–6] and charge density fluctuations [7–11], spin density waves (SDWs) [12,13], electronic nematicity [14–16], orbital currents [17,18], and possibly an unconventional spatially modulated Cooper pair density [19,20].

Because of this complexity, new experimental strategies are needed to control the interactions and emergent properties and to establish the hierarchy between cause and effect among the different orders [21].

A common approach, used to tune the local properties of cuprate HTSs, is to grow them in thin-film form. The epitaxial strain induced by the substrate has been used to control the atomic positions and therefore the strengths of the interactions. More in general, strain allows one to control the critical temperature [22], as well as the magnetic-exchange interaction [23], the nematicity [16,24], and the charge density waves [25–29].

The ultimate manipulation of the HTS cuprates could be represented by the confinement of the CuO<sub>2</sub> planes on the nanoscale—a realm which is still largely unexplored. In this limit, possibly degenerate ground states, different from those of the corresponding bulk, could become favorable. A way to confine the CuO<sub>2</sub> planes is to grow high-quality

\*riccardo.arpaia@chalmers.se

†Present address: Department of Energy Conversion and Storage, Technical University of Denmark, DK-2800 Kongens Lyngby, Denmark.

‡floriana.lombardi@chalmers.se

Published by the American Physical Society under the terms of the Creative Commons Attribution 4.0 International license. Further distribution of this work must maintain attribution to the author(s) and the published article's title, journal citation, and DOI. Funded by Bibsam.

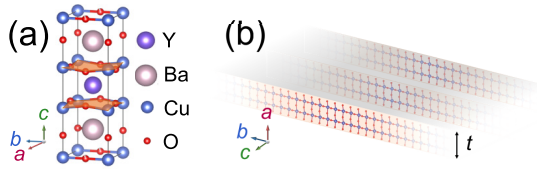


FIG. 1.  $\text{CuO}_2$  nanoribbons from YBCO. (a) YBCO unit cell. The  $\text{CuO}_2$  planes where superconductivity, as well as various electronic local orders, reside, are highlighted in orange. (b) By growing  $a$ -axis oriented YBCO films, the  $\text{CuO}_2$  planes form ribbons of nanometer width, confined in one direction by the film thickness  $t$ .

$a$ -axis oriented thin films. In  $a$ -axis films, the  $\text{CuO}_2$  planes, hosting superconductivity, are constrained in one direction by the thickness of the film and are hence shaped into a quasi-one-dimensional geometry, effectively forming  $\text{CuO}_2$  ribbons of nanometer width, perpendicular to the substrate [see Fig. 1(b)]. One can expect that this confinement influences the properties of the nanoscale ordering phenomena, whose characteristic lengths are comparable with the lateral dimensions of the  $\text{CuO}_2$  ribbons [4,19,30].

The growth of high-quality epitaxial  $a$ -axis films is however challenging: differently from the  $c$ -axis counterpart,  $a$ -axis grains nucleate at rather low deposition temperatures [31], which favor the growth of less homogeneous films, with poor crystallinity [32]. Despite considerable efforts to produce optimally doped films and heterostructures of high quality [33–50], the impact of  $\text{CuO}_2$  confinement on the cuprate phase diagram requires the growth of underdoped films, where the majority of local orders manifest [1,2]. Therefore, achieving controlled variation of the doping level is crucial, while maintaining the anisotropic characteristics of the bulk material, i.e., growing fully detwinned samples. These tasks are challenging even for  $c$ -axis oriented films and have never been successfully executed with  $a$ -axis oriented films.

We have previously reported the growth of high-quality optimally doped  $a$ -axis oriented  $\text{YBa}_2\text{Cu}_3\text{O}_{7-\delta}$  (YBCO) thin films [48]. In this work we present the properties of  $a$ -axis oriented YBCO thin films, at various doping levels from the optimally doped down to the insulating state, obtained by a careful oxygen annealing procedure. X-ray diffraction (XRD) analysis shows that the films are fully detwinned, implying the presence of  $\text{CuO}$  chains, aligned throughout the sample along the in-plane  $b$  direction. By varying the film thickness up to 800 nm, we have verified the dominant role of strain in this peculiar system. We find that the unit cell differs from the bulk even at dimensions of several hundred nanometers. The resistance vs temperature measurements are characterized by sharp superconducting transitions, showing that the superconducting properties of the films are rather homogeneous. We observe a strong in-plane anisotropy of the resistance, comparable, also for rather thick films, to the best results achieved on detwinned single crystals. This opens up the possibility of studying potential modifications of the ground state induced by confinement in films of only a few unit cells' thickness.

## II. THIN-FILM GROWTH AND ROLE OF THE OXYGEN ANNEALING

To favor the growth of  $a$ -axis oriented films, we have deposited by rf sputtering, at a power of 50 W and pressure of 0.1 mbar ( $\text{Ar} : \text{O}_2 = 4 : 1$ ), a 90 nm thick film of  $\text{PrBa}_2\text{Cu}_3\text{O}_{7-y}$  (PBCO), acting as an insulating buffer layer, on a (100)  $\text{SrLaGaO}_4$  (SLGO) substrate [51]. The temperature is gradually increased during the deposition from 660 °C, where the first nuclei are formed, up to 830 °C. After the deposition of this buffer layer, which is known to promote the growth of homogeneous  $a$ -axis superconducting films, with high crystallinity [36,39], the sample is transferred *in situ* to a pulsed laser deposition chamber. Here, a YBCO film, with a thickness varying in the range 50–800 nm, is deposited at 805 °C and an oxygen pressure of 0.9 mbar. By slowly decreasing the temperature after the deposition, at an oxygen pressure of 900 mbar, we achieve slightly overdoped films where the  $\text{CuO}$  chains are fully oxidized. The next step to obtain underdoped films is the removal of oxygen from the  $\text{CuO}$  chains, so to get access to the underdoped side of the YBCO phase diagram. In the case of  $c$ -axis oriented YBCO films, we have succeeded by carefully tuning the *in situ* postannealing, i.e., cooling down the film soon after the deposition at a 5°/min rate, with an oxygen pressure reduced from 900 mbar down to  $1 \times 10^{-5}$  mbar, depending on the required doping level [52,53]. We have applied this procedure to the  $a$ -axis oriented films, and performed a transport characterization via resistance vs temperature  $R(T)$  measurements. A typical result, for a 300 nm thick film *in situ* annealed at a pressure of  $1 \times 10^{-3}$  mbar, is shown in Fig. 2(a). The zero resistance critical temperature is reduced down to 50 K, as expected for an underdoped film. However, the onset of the superconducting transition is at

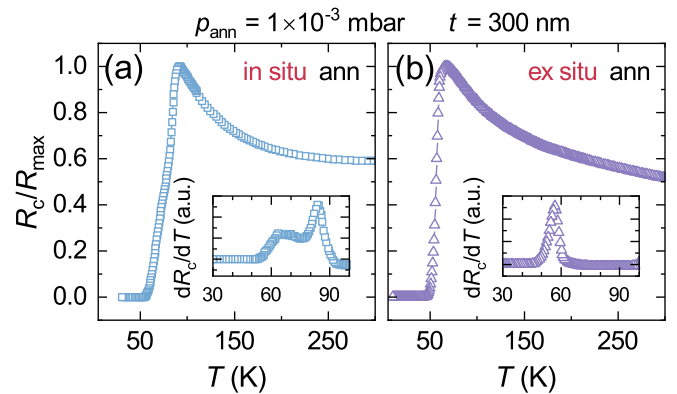


FIG. 2. Dependence of the superconducting transition of  $a$ -axis YBCO thin films on the oxygen annealing. (a) The resistance measured along the  $c$ -axis direction,  $R_c$ , normalized to the maximum value  $R_{\text{max}}$ , is plotted vs temperature for a 300 nm thick underdoped film, achieved using an *in situ* annealing oxygen pressure  $p_{\text{ann}} = 1 \times 10^{-3}$  mbar. In the inset, the derivative of the  $R_c(T)$  highlights the pronounced broadening of the superconducting transition. (b)  $R_c(T)$  is presented for an underdoped film, obtained by applying the same annealing pressure used for the film in panel (a), but *ex situ*. The homogeneity of the film is proven by a rather sharp superconducting transition, as highlighted in the inset.

$T \sim 91$  K, which hints at the presence of residual optimally doped domains. Therefore this annealing procedure, that we have successfully used for  $c$ -axis oriented YBCO films, cannot be implemented for  $a$ -axis oriented YBCO films, since it leads to films with inhomogeneous doping. The result is not surprising, considering the nanoribbon-like structure of the  $a$ -axis films: the oxygen planes are strongly exposed to the environment, which alter the oxygen diffusion conditions for achieving a homogeneous oxygen content across the whole film [54–56]. Here it is worth mentioning that performing a longer *in situ* annealing at an intermediate temperature during the cooling does not improve the superconducting properties and the sample homogeneity. To overcome this issue, we have used an alternative approach, already successfully employed in modifying the oxygen doping in  $c$ -axis oriented films [57]: starting from a high-quality slightly overdoped film, we decrease the oxygen doping with a separate step. The annealing, which changes the oxygen doping, is performed *ex situ*, in a reduced oxygen pressure (in the range of  $10^{-5}$  to  $10^2$  mbar, depending on the desired doping level) for 9 h at  $650^\circ\text{C}$ . Keeping a constant pressure, the film is subsequently cooled down to room temperature using a constant cooling rate of  $5^\circ/\text{min}$ . Figure 2(b) shows the results of this procedure: the film, annealed *ex situ* using the same oxygen pressure as the film shown in Fig. 2(a), presents instead a rather sharp superconducting transition, reflecting the high level of homogeneity of the sample.

This latter procedure offers the advantage to be able to modify the doping of the same film several times. The whole underdoped side of the phase diagram can therefore be explored using a single sample, in which only the oxygen content is modified.

### III. STRUCTURAL CHARACTERIZATION: COMPLETE DETWINNING AND STRAIN-INDUCED ORTHORHOMBICITY

A thorough XRD analysis has been performed using a four-circle Panalytical X’pert diffractometer with  $\text{CuK}\alpha$  radiation ( $\lambda = 1.5406 \text{ \AA}$ ), incorporating a hybrid Ge(220) monochromator and a PIXcel 3D detector matrix. The primary objective of the analysis is to determine the structural properties of the *ex-situ*-annealed underdoped  $a$ -axis films.

The symmetrical  $2\theta$ - $\omega$  scans [see Fig. 3(a)] confirm what has been previously observed on the as-grown, fully oxygenated films, i.e., that the films are highly crystalline and  $a$ -axis oriented, with a negligible contribution coming from possible  $c$ -axis oriented grains. The homogeneity of the films is doping independent, as proved by the full width at half maximum (FWHM) of the (300) YBCO Bragg peak,  $\Delta 2\theta^{(300)}$ , which remains constant from the slightly overdoped down to the undoped region [see left inset of Fig. 3(a)].

To get more insight into the twinning state of these systems, we have performed symmetrical  $2\theta$ - $\omega$  maps in the  $2\theta$

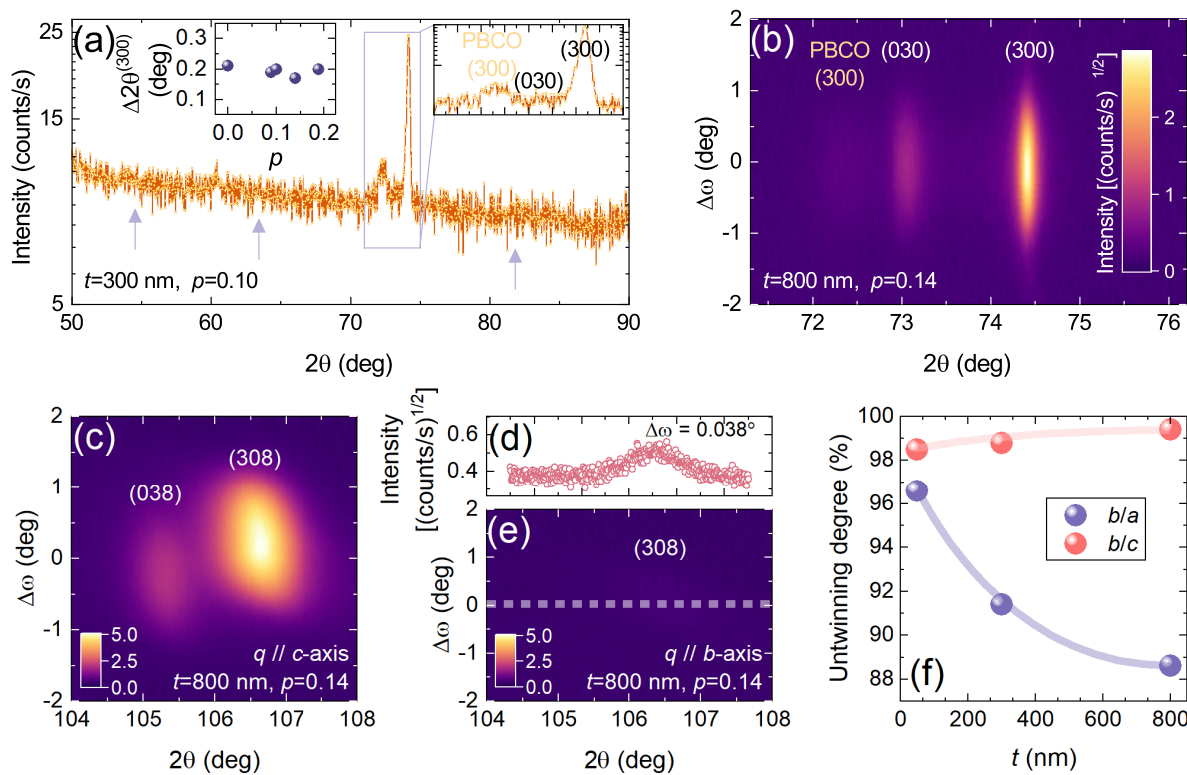


FIG. 3. Complete detwinning in  $a$ -axis oriented YBCO films. (a) Symmetrical  $2\theta$ - $\omega$  scan of a 300 nm thick underdoped film. The arrows show the positions where the  $(00n)$  YBCO reflections should be for a  $c$ -axis oriented film. The inset on the left shows the FWHM of the (300) YBCO Bragg peak,  $\Delta 2\theta^{(300)}$ , as a function of  $p$ . (b) Symmetrical  $2\theta$ - $\omega$  map of a 800 nm, slightly underdoped YBCO film. Asymmetrical  $2\theta$ - $\omega$  maps on the same sample are performed with the momentum  $q$  parallel either to (c) the  $c$ -axis or to (d), (e) the  $b$ -axis direction. Panel (d) is the line scan, highlighted in panel (e) by the dashed line. (f) The untwining degree, determined by the intensity of the measured Bragg peaks, is plotted as a function of the film thickness.

TABLE I. Summary of the lattice parameters, related to the 300 nm thick YBCO films, extracted from the maps in Fig. 5. In parentheses, the bulk lattice parameters of YBCO (from [62]) and PBCO (from [63] and [64] respectively for the undoped and doped compound) are reported. In the last column, the volume  $abc$  of the various unit cells is reported, confirming the Poisson effect in our samples.

Material	$a$ (Å)	$b$ (Å)	$c$ (Å)	$V$ (Å <sup>3</sup> )
SrLaGaO <sub>4</sub>	3.842	3.842	12.678	187.140
PrBa <sub>2</sub> Cu <sub>3</sub> O <sub>6</sub>	3.915 (3.906)	3.890 (3.906)	11.88 (11.824)	180.92 (180.40)
PrBa <sub>2</sub> Cu <sub>3</sub> O <sub>7</sub>	3.916 (3.913)	3.885 (3.916)	11.76 (11.712)	178.91 (179.46)
YBa <sub>2</sub> Cu <sub>3</sub> O <sub>6</sub>	3.848 (3.86)	3.869 (3.86)	11.82 (11.817)	175.98 (176.07)
YBa <sub>2</sub> Cu <sub>3</sub> O <sub>7</sub>	3.825 (3.819)	3.885 (3.886)	11.68 (11.68)	173.57 (173.34)

region around the (300) peaks of PBCO and YBCO [see Fig. 3(a)]. A third peak is visible, at intermediate angles between these two, whose intensity grows when the film thickness increases. This is the (030) YBCO reflection, associated to the  $b$  axis: a small fraction of the  $a$  and  $b$  axis is randomly exchanged; i.e., a small  $a$ - $b$  twinning occurs. We get confirmation of that, performing asymmetrical  $2\theta$ - $\omega$  maps around the (038)-(308) YBCO reflections along the  $c$ -axis direction [see Fig. 3(c)], and ascertaining the presence of a rather weak (038) peak. Rotating the sample by 90 degrees, and performing the same measurement along the  $b$ -axis direction, an extremely weak (308) reflection appears [see Figs. 3(d) and 3(e)]. In this configuration, the detection of any ( $\ell 0 n$ ) Bragg peaks should be forbidden, since the scattering plane has no component along the  $c$ -axis direction. This unexpected peak is therefore related to a random exchange, a twinning, of the  $b$  and  $c$  axis. From the intensity of the YBCO reflections in the symmetrical and asymmetrical maps, we have calculated the detwinning degrees as a function of the film thickness [see Fig. 3(f)]. The detwinning  $b/c$  is thickness independent, and close to 99%. The detwinning  $b/a$  gets instead smaller by increasing the film thickness from 50 to 800 nm, going from  $\sim 97\%$  to  $\sim 88\%$ . In particular for the thinnest films, this corresponds to a nearly complete detwinning, comparable to that in single crystals, and better than any result achieved so far for YBCO thin films [58–60].

From the positions of the YBCO reflections in the symmetrical and asymmetrical maps, we have extracted information about the structure of the thin films and on the modification of the unit cell induced by the strain and by confinement effects. The length of the  $c$ -axis parameter increases as the *ex situ* oxygen pressure is decreased. This proves that our process is effective in varying the oxygen concentration within the films. The doping  $p$  can therefore be estimated, by the combined knowledge of the  $c$ -axis parameter and of the  $T_c$ , using a procedure already successfully used for YBCO single crystals [61] and thin films [52]. Finally, we can plot the  $a$ -,  $b$ -, and  $c$ -axis lengths vs  $p$  [see Figs. 4(a) and 4(b)]. The YBCO  $c$  axis is relaxed, with a length almost coinciding with the bulk value [62] already at a thickness of 50 nm. When reducing the oxygen doping, a remarkable effect of the strain on the YBCO  $a$ - and  $b$ -axis parameter occurs. The orthorhombic to tetragonal transition, usually happening below  $p \sim 0.06$  [62], is indeed absent. This is evident already from the symmetrical  $2\theta$ - $\omega$  scans [see Figs. 4(c) and 4(d)]: comparing an insulating to a slightly underdoped sample, one can notice that the (030) and (300) peak positions get much closer in the undoped case, but are still distinct.

To comprehensively address the strain mechanism in our films, at the origin of the suppression of the orthorhombic to tetragonal transition, we have examined two extreme doping cases, namely, near-zero doping and a doping level of 0.18. For each of these two samples, we conducted reciprocal space maps (RSMs) of the (200), (309), and (330) reflections of SLGO, PBCO, and YBCO (see Fig. 5), which also provided insights into the lattice parameters of the different layers (see Table I).

The symmetric RSMs in Figs. 5(a) and 5(b) show a perfect alignment of the YBCO (200) and PBCO (200) reflections with the SLGO (200) reflection at both doping levels, which supports the high texture of the films.

With knowledge of the out-of-plane  $a$ -axis parameter for both PBCO and YBCO, we determined the in-plane parameters and strain conditions by performing RSMs of the asymmetrical (309) [see Figs. 5(c) and 5(d)] and (330) [see Figs. 5(e) and 5(f)] reflections. The maps confirm the pivotal role of the PBCO layer in determining the final crystal structure of the YBCO film. First, the PBCO  $c$ -axis parameter mediates the tension between the substrate and the YBCO layer, accommodating the significant strain along the in-plane [001] direction (with a lattice mismatch of about 7%–8% between substrate and film). As we can see in Figs. 5(c) and 5(d), the PBCO layer exhibits a tensile strain along this direction, resulting in a broad (309) reflection, indicative of a mosaic structure, with the  $c$ -axis parameter expanding by 0.5% relative to bulk values. This allows the relaxation of the YBCO  $c$  axis toward bulk parameters at any doping levels [as also observed in Fig. 4(a)], reducing the mosaicity along that direction. Second, the PBCO  $b$ -axis parameter significantly influences the final structure of the YBCO layer. This occurs because its length is close to, though slightly longer than, those of SLGO and YBCO, and weakly doping-dependent compared to the YBCO  $b$  axis. Independently of the doping level, the PBCO  $b$  axis is compressively strained by the substrate to a value ( $b = 3.89$  Å) that is very close to that of slightly overdoped YBCO. Consequently, a doping-dependent strain is induced by the PBCO into the YBCO layer. In the  $p = 0.18$  sample [see Fig. 5(f)], the PBCO and YBCO (330) reflections have almost identical  $q_{[010]}$  component: the YBCO  $b$  axis is subject to a tiny strain and preserves its bulk value. In the undoped sample [see Fig. 5(e)], the tensile strain applied by the PBCO layer maintains the YBCO  $b$  axis longer than the  $a$  axis (which undergoes shrinkage due to the Poisson effect; see Table I), leading to the disappearance of the orthorhombic-to-tetragonal transition. This evidence is clearly depicted in Fig. 5(e), where the YBCO (330) reflection remains notably

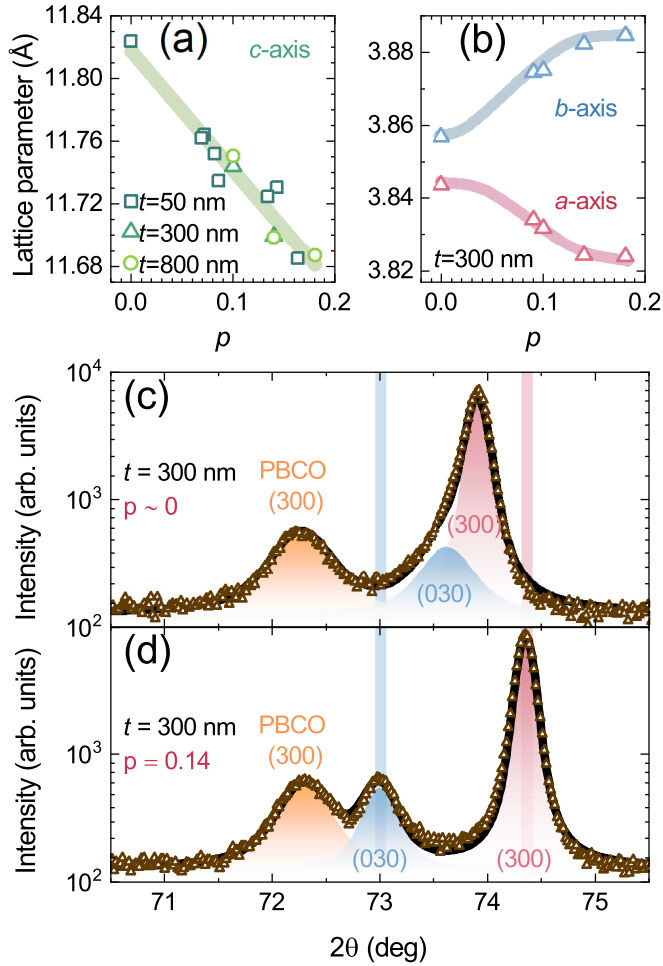


FIG. 4. Locking of the  $\text{CuO}_2$  planes in  $a$ -axis oriented YBCO films. (a) The  $c$ -axis parameter, extracted from the  $(\ell 00)$  and  $(\ell 0n)$  Bragg reflections, is shown as a function of the doping  $p$  for films of different thickness. For each sample,  $p$  has been determined based on the  $c$ -axis length, and then utilizing the critical temperature  $T_c$  measured via transport (see Sec. IV) and the empirical parabolic relationship connecting doping and  $T_c$  in cuprate HTS [52,61]. Notably, all data points for the 50 nm thickness have been collected from a single, multiply annealed thin film. (b) The  $a$ - and  $b$ -axis parameters, extracted from the  $(\ell 00)$  and  $(\ell m0)$  Bragg reflections, are plotted vs  $p$  for different 300 nm thick films. (c), (d) The symmetrical  $2\theta$ - $\omega$  scans respectively of an insulating ( $p \sim 0$ ) and of an underdoped ( $p = 0.14$ ) film are compared. The decomposition of the data into three Voigt profiles associated to the (300) PBCO, the (030) YBCO, and the (300) YBCO reflections shows first that the PBCO layer is unaffected by the annealing procedure, as the peak position is unchanged vs doping, and second, that the two YBCO peaks, related to the  $\text{CuO}_2$  planes, are distinct, even though they get closer, in the undoped sample. To facilitate the comparison, the vertical bars show the position of the two YBCO peaks in the doped sample.

distant from the dashed line corresponding to the tetragonal line  $a = b$ . In conclusion, the strain has important consequences on the crystal structure: the  $\text{CuO}_2$  planes, which are confined by the nanoscale film thickness along  $a$ , are also influenced by the substrate and seed layer, which lock the value of the  $b$  axis. What is remarkable is that this locking also occurs in films, with thicknesses significantly exceeding

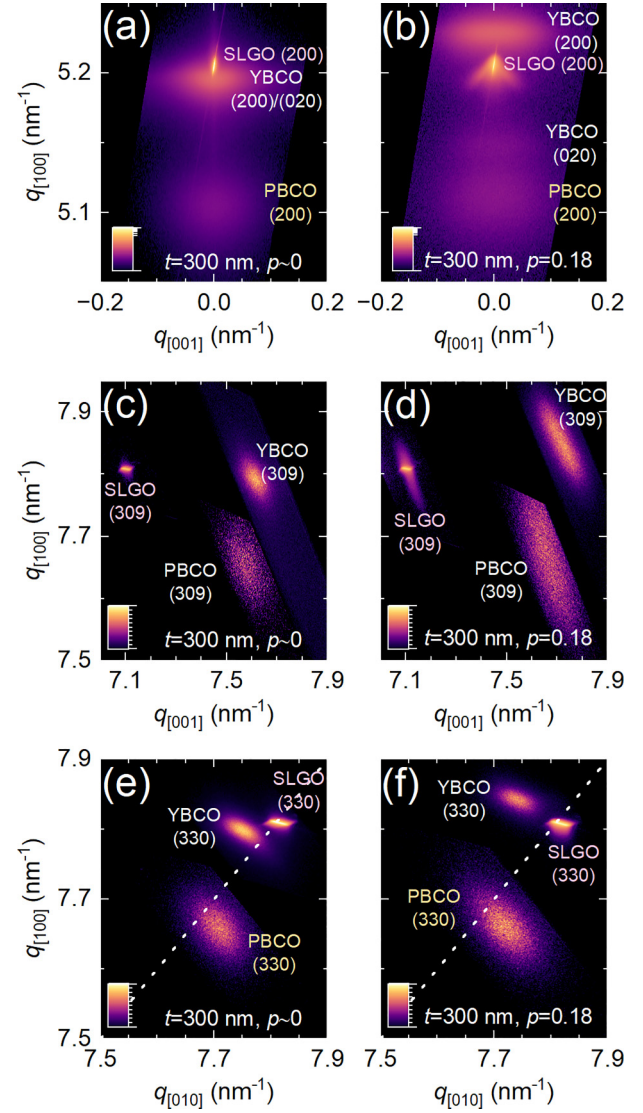


FIG. 5. Suppression of the orthorhombic to tetragonal transition. (a), (b) Symmetric and (c)–(f) asymmetric RSMs of two 300 nm thick  $a$ -axis oriented YBCO films. Panels (a), (c), (e) refer to an undoped sample, while panels (b), (d), (f) refer to a fully oxygenated sample. (a), (b) Symmetric map of the (200) reflections of the SLGO, PBCO, and YBCO. (c), (d) Asymmetric map of the (309) reflections of the SLGO, PBCO, and YBCO. (e), (f) Asymmetric map of the (330) reflections of the SLGO, PBCO, and YBCO. In panels (e) and (f), the dashed line represents the tetragonal line  $a = b$ . The  $a$ ,  $b$ , and  $c$  axis parameters can be determined from the RSM peaks via  $a = \ell/q_{[100]}$ ,  $b = m/q_{[010]}$ , and  $c = n/q_{[001]}$ , where  $\ell$ ,  $m$ , and  $n$  are the Miller indices of the peak  $(\ell mn)$ .

the relaxation threshold observed in  $c$ -axis oriented YBCO films [65] [see Figs. 4(b) and 5(e)].

#### IV. TRANSPORT CHARACTERIZATION

To measure the resistance vs temperature  $R(T)$  along the two in-plane directions of the films, we employed very elongated Hall-bar-like structures (see Fig. 6), realized by a soft patterning procedure we have developed over years for various cuprate HTSs [48,53,66]. The current is applied at the two

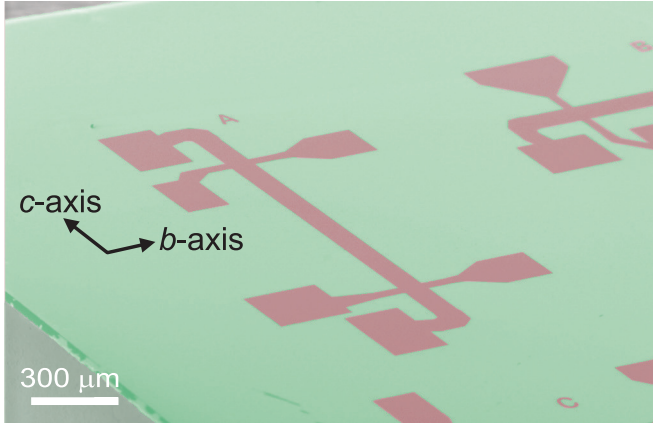


FIG. 6. Scanning electron microscopy image of the structures used for the measurements of the nanoribbon resistivity. The 1 mm long and 100  $\mu\text{m}$  wide Hall bars are oriented along either the  $b$ -axis or the  $c$ -axis direction of the YBCO film.

extremities of the bars, with the two voltage probes positioned 10 squares apart. The choice of this geometry is motivated by the high in-plane resistivity anisotropy expected in our films, due to the weak coupling between adjacent  $\text{CuO}_2$  planes, i.e., along the  $c$ -axis direction. Consequently, the standard van der Pauw method [67], which assumes isotropic resistivity and homogeneous resistivity distribution, cannot be applied.

We have performed our measurements on samples with thicknesses in the range between 50 and 800 nm, and with doping levels going from the undoped up to the slightly overdoped. In the following, we will focus however only on the results related to the 300 nm thick films. An overview of the resistivity measurements vs temperature along the  $b$ -axis direction,  $R_b(T)$ , is shown in Figs. 7(a)–7(c). The curves refer to different doping levels and are characterized by rather sharp superconducting transitions and by a normal state resistance, qualitatively following the typical dependencies observed in  $c$ -axis oriented films [see Fig. 7(d)] [52,57,68–70]. This refers in particular to the doping-dependent crossover temperature  $T_L$ , inferred by the departure from the linear-in- $T$  behavior of the resistance at high temperature, which appears as a sort of boundary between the unconventional strange metal phase and a region where the material loses low-energy electronic excitations (the pseudogap region). A summary of the parameters extracted for the films of Fig. 7 is shown in Table II.

Figure 8 shows instead the  $R(T)$ , along both the in-plane directions, of a typical 300 nm thick film, at a doping level ( $p \sim 0.09$ ) where the  $\text{CuO}_2$  planes—here confined at the nanoscale—have been shown to host both spin [12] and charge density waves [4]. In the normal state, a resistivity anisotropy much stronger than in optimally doped YBCO ( $R_c/R_b \approx 60$  at room temperature [71,72]) is present. This is expected, as a consequence of the weaker coupling between the  $\text{CuO}_2$  planes, occurring in the underdoped regime because of the increased  $c$ -axis length, i.e., of the increased distance between the planes. In our case, at room temperature,  $R_c/R_b \approx 70$  for the optimally doped films; when decreasing the oxygen doping,  $R_c$  becomes  $\sim 100$  times larger than  $R_b$ . This anisotropy, comparable to the best results on detwinned single crystals [72,73], is reported for the first time in

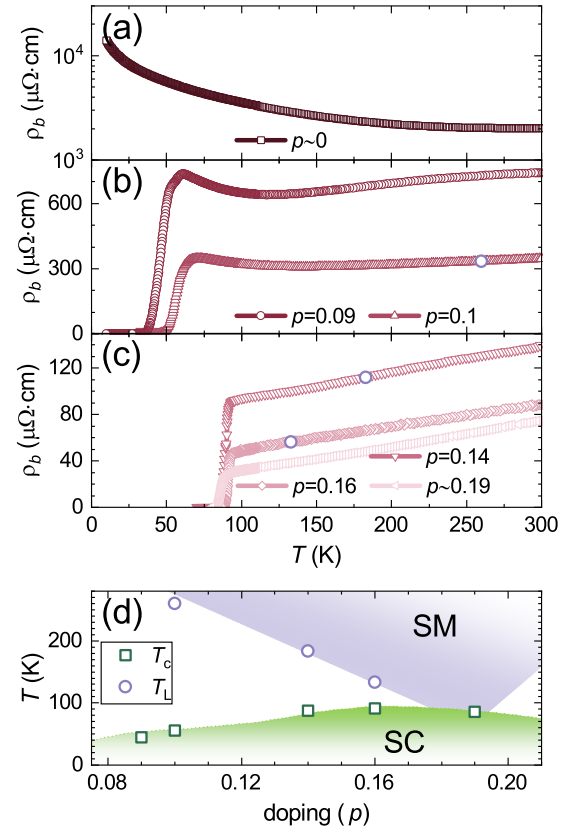


FIG. 7. Doping dependence of nanoribbon resistivity. Panels (a)–(c) show  $\rho_b(T)$  for various 300 nm thick films at different oxygen doping levels. The critical temperature  $T_c$  for each film is determined from the maximum of the first derivative of  $\rho_b(T)$ .  $T_L$  (violet circles), marking the crossover between the pseudogap region and the strange metal phase, is the temperature below which the resistivity  $\rho_b(T)$  deviates by 1% from the high-temperature linear fit of the curves, performed in the interval  $280 \text{ K} < T < 300 \text{ K}$ . Notably, all  $\rho_b(T)$  datasets are extensive, featuring a sub-Kelvin temperature step size. Panel (d) presents a phase diagram constructed from the obtained values of  $T_c$  and  $T_L$ , exhibiting good agreement with the superconducting (SC) and strange metal (SM) regions observed in YBCO single crystals and  $c$ -axis oriented films [52,68].

TABLE II. Summary of the parameters related to the 300 nm thick films presented in Fig. 7. The films have been achieved by varying the *ex situ* annealing pressure  $p_{\text{ann}}$  across a seven orders of magnitude range, spanning from fully oxygenated to undoped samples. From the  $R(T)$  of the films at different doping levels we have extracted  $T_c$  and  $T_L$ , following the procedure described in the caption of Fig. 7. Finally, for each film the doping level  $p$  has been determined by the combined knowledge of  $T_c$  and of the  $c$ -axis length [11,52,61].

$p_{\text{ann}}$ (mbar)	$T_c$ (K)	$T_L$ (K)	$p$
$6.0 \times 10^{-5}$		(> 280)	0
$3.2 \times 10^{-4}$	45	(> 280)	0.09
$1.0 \times 10^{-3}$	56	260	0.10
$1.1 \times 10^{-2}$	88	183	0.14
$1.0 \times 10^0$	91	133	0.16
$9.0 \times 10^2$	86		0.19

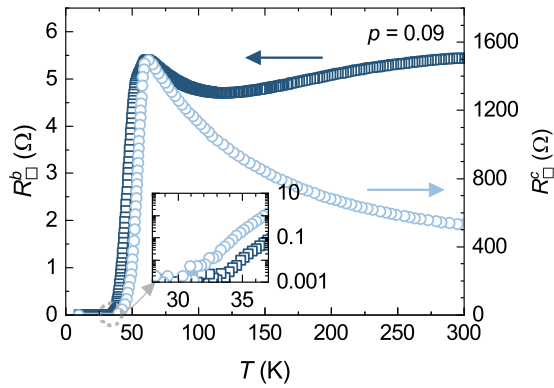


FIG. 8. Anisotropic transport properties of underdoped 300 nm thick  $\text{CuO}_2$  nanoribbons. Sheet resistances  $R_{\square}^b(T)$  (squares) and  $R_{\square}^c(T)$  (circles) of an underdoped ( $p = 0.09$ ) film. The inset, where the tails of the superconducting transition of the two measurements are presented on the same vertical scale, highlights the lower zero resistance critical temperature occurring along the  $c$  axis.

underdoped  $a$ -axis oriented YBCO thin films. This suggests that the coupling between adjacent  $\text{CuO}_2$  planes is weak already in rather thick films, as also highlighted by the insulator-like temperature dependence of  $R_c$ , and that it can be possibly made even weaker in few-unit-cell-thick films, where the effect of the confinement is enhanced.

Furthermore, as shown in the inset of Fig. 8, the zero resistance critical temperature is also anisotropic, being lower along the  $c$ -axis direction. This suggests a weaker interlayer Josephson coupling along the  $c$  axis, reminiscent of the observations in underdoped “214” cuprates like  $\text{La}_{2-x}\text{Ba}_x\text{CuO}_4$  [74]. In this rather special cuprate family, this occurrence has been theoretically associated to the formation of stripes, where CDWs and SDWs are coupled, and to the presence of pair density waves [20]. The appearance of a similar phenomenology in YBCO might indicate the potential influence of confinement on the material ground state, with modified CDWs and SDWs compared to the bulk. The investigation of these local orders in underdoped  $\text{CuO}_2$  nanoribbons will be object of future work, extending beyond the scope of the present study.

## V. CONCLUSIONS

We have presented the fabrication and characterization of underdoped  $\text{CuO}_2$  nanoribbons, realized by employing  $a$ -axis oriented YBCO thin films. The oxygen doping is tuned by using an *ex situ* annealing procedure, which allows the achievement of films covering a broad region of the HTS phase diagram, going from the undoped insulator

up to the slightly overdoped level. Taking advantage of the fast oxygen diffusion in the  $a$ - $b$  planes, which are open in our films, this procedure demonstrates its effectiveness to vary the oxygen doping up to high thicknesses (of the order of 800 nm). Structural XRD characterization demonstrates that the films are nearly totally detwinned, and the strain affects the crystal structure, up to the largest investigated thickness: the  $\text{CuO}_2$  planes have a nanoribbon shape, which inhibits the orthorhombic-to-tetragonal transition and possibly induces the system to be more anisotropic than in the bulk. The homogeneity of the films has been demonstrated by  $R(T)$  measurements, showing rather narrow superconducting transitions. The transport properties exhibit notable in-plane anisotropy in both normal state resistance and critical temperature, indicative of weak coupling between the  $\text{CuO}_2$  planes.

The system we have engineered, where  $\text{CuO}_2$  planes are confined into nanoribbons, stands out as a natural candidate for studying local orders in HTSs at the nanoscale. In this setting, the effects of strain and confinement may simplify the underlying physics, offering valuable insights into the intricacies of these materials.

More in general, this platform holds significant promise for advancing the understanding of HTSs in both fundamental physics and practical applications. In terms of basic physics,  $a$ -axis oriented films are inherently suitable for pump probe experiments. The intense electric field of mid-infrared light pulses can align with the crystallographic  $c$  axis, which overcomes limitations in  $c$ -axis oriented samples, where electric field interactions are restricted to in-plane excitations. The electronic structure of cuprates and the position of apical oxygen atoms get therefore strongly altered [75], which can provide valuable insights into the phenomenology behind light-induced superconductivity [76]. On the practical side, films oriented along the  $a$  axis, where the superconducting coherence length is approximately an order of magnitude longer than along the  $c$  axis, offer an ideal system for fabricating high-performance Josephson junctions, which are crucial components for superconducting electronics applications [77,78].

## ACKNOWLEDGMENTS

The authors acknowledge Andrea Cavalleri and Michael Först for insightful discussions and Henrik Frederiksen for technical support. This work was performed in part at Myfab Chalmers, and is supported by the Area of Advance Nano program at Chalmers, the 2D Tech VINNOVA Competence Center (Grant No. 2019-00068), and the Swedish Research Council (VR) under Projects No. 2020-04945 (R.A.), No. 2020-05184 (T.B.), and No. 2022-04334 (F.L.).

- [1] B. Keimer, S. A. Kivelson, M. R. Norman, S. Uchida, and J. Zaanen, From quantum matter to high-temperature superconductivity in copper oxides, *Nature (London)* **518**, 179 (2015).
- [2] E. Fradkin, S. A. Kivelson, and J. M. Tranquada, Colloquium: Theory of intertwined orders in high temperature superconductors, *Rev. Mod. Phys.* **87**, 457 (2015).

- [3] B. Loret, N. Auvray, Y. Gallais, M. Cazayous, A. Forget, D. Colson, M.-H. Julien, I. Paul, M. Civelli, and A. Sacuto, Intimate link between charge density wave, pseudogap and superconducting energy scales in cuprates, *Nat. Phys.* **15**, 771 (2019).
- [4] G. Ghiringhelli, M. Le Tacon, M. Minola, S. Blanco-Canosa, C. Mazzoli, N. Brookes, G. De Luca, A. Frano, D. Hawthorn,

- F. He *et al.*, Long-range incommensurate charge fluctuations in (Y,Nd)Ba<sub>2</sub>Cu<sub>3</sub>O<sub>6+x</sub>, *Science* **337**, 821 (2012).
- [5] J. Chang, E. Blackburn, A. Holmes, N. B. Christensen, J. Larsen, J. Mesot, R. Liang, D. Bonn, W. Hardy, A. Watenphul *et al.*, Direct observation of competition between superconductivity and charge density wave order in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>6.67</sub>, *Nat. Phys.* **8**, 871 (2012).
- [6] S. Gerber, H. Jang, H. Nojiri, S. Matsuzawa, H. Yasumura, D. Bonn, R. Liang, W. Hardy, Z. Islam, A. Mehta *et al.*, Three-dimensional charge density wave order in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>6.67</sub> at high magnetic fields, *Science* **350**, 949 (2015).
- [7] R. Arpaia, S. Caprara, R. Fumagalli, G. De Vecchi, Y. Peng, E. Andersson, D. Betto, G. De Luca, N. Brookes, F. Lombardi *et al.*, Dynamical charge density fluctuations pervading the phase diagram of a Cu-based high- $T_c$  superconductor, *Science* **365**, 906 (2019).
- [8] B. Yu, W. Tabis, I. Bialo, F. Yakhou, N. B. Brookes, Z. Anderson, Y. Tang, G. Yu, and M. Greven, Unusual dynamic charge correlations in simple-tetragonal HgBa<sub>2</sub>CuO<sub>4+δ</sub>, *Phys. Rev. X* **10**, 021059 (2020).
- [9] R. Arpaia and G. Ghiringhelli, Charge order at high temperature in cuprate superconductors, *J. Phys. Soc. Jpn.* **90**, 111005 (2021).
- [10] H. Y. Huang, A. Singh, C. Y. Mou, S. Johnston, A. F. Kemper, J. van den Brink, P. J. Chen, T. K. Lee, J. Okamoto, Y. Y. Chu, J. H. Li, S. Komiya, A. C. Komarek, A. Fujimori, C. T. Chen, and D. J. Huang, Quantum fluctuations of charge order induce phonon softening in a superconducting cuprate, *Phys. Rev. X* **11**, 041038 (2021).
- [11] R. Arpaia, L. Martinelli, M. M. Sala, S. Caprara, A. Nag, N. B. Brookes, P. Camisa, Q. Li, Q. Gao, X. Zhou *et al.*, Signature of quantum criticality in cuprates by charge density fluctuations, *Nat. Commun.* **14**, 7198 (2023).
- [12] D. Haug, V. Hinkov, Y. Sidis, P. Bourges, N. B. Christensen, A. Ivanov, T. Keller, C. Lin, and B. Keimer, Neutron scattering study of the magnetic phase diagram of underdoped YBa<sub>2</sub>Cu<sub>3</sub>O<sub>6+x</sub>, *New J. Phys.* **12**, 105006 (2010).
- [13] Y. Li, V. Balédent, N. Barišić, Y. C. Cho, Y. Sidis, G. Yu, X. Zhao, P. Bourges, and M. Greven, Magnetic order in the pseudogap phase of HgBa<sub>2</sub>CuO<sub>4+δ</sub> studied by spin-polarized neutron diffraction, *Phys. Rev. B* **84**, 224508 (2011).
- [14] S. A. Kivelson, E. Fradkin, and V. J. Emery, Electronic liquid-crystal phases of a doped Mott insulator, *Nature (London)* **393**, 550 (1998).
- [15] R. Daou, J. Chang, D. LeBoeuf, O. Cyr-Choiniere, F. Laliberté, N. Doiron-Leyraud, B. Ramshaw, R. Liang, D. Bonn, W. Hardy *et al.*, Broken rotational symmetry in the pseudogap phase of a high- $T_c$  superconductor, *Nature (London)* **463**, 519 (2010).
- [16] J. Wu, A. Bollinger, X. He, and I. Božović, Spontaneous breaking of rotational symmetry in copper oxide superconductors, *Nature (London)* **547**, 432 (2017).
- [17] B. Fauqué, Y. Sidis, V. Hinkov, S. Pailhes, C. T. Lin, X. Chaud, and P. Bourges, Magnetic order in the pseudogap phase of high- $T_c$  superconductors, *Phys. Rev. Lett.* **96**, 197001 (2006).
- [18] C. M. Varma, Colloquium: Linear in temperature resistivity and associated mysteries including high temperature superconductivity, *Rev. Mod. Phys.* **92**, 031001 (2020).
- [19] M. Hamidian, S. Edkins, S. H. Joo, A. Kostin, H. Eisaki, S. Uchida, M. Lawler, E.-A. Kim, A. Mackenzie, K. Fujita *et al.*, Detection of a Cooper-pair density wave in Bi<sub>2</sub>Sr<sub>2</sub>CaCu<sub>2</sub>O<sub>8+x</sub>, *Nature (London)* **532**, 343 (2016).
- [20] D. F. Agterberg, J. Davis, S. D. Edkins, E. Fradkin, D. J. Van Harlingen, S. A. Kivelson, P. A. Lee, L. Radzihovsky, J. M. Tranquada, and Y. Wang, The physics of pair-density waves: Cuprate superconductors and beyond, *Annu. Rev. Condens. Matter Phys.* **11**, 231 (2020).
- [21] C. Ahn, A. Cavalleri, A. Georges, S. Ismail-Beigi, A. J. Millis, and J.-M. Triscone, Designing and controlling the properties of transition metal oxide quantum materials, *Nat. Mater.* **20**, 1462 (2021).
- [22] J.-P. Locquet, J. Perret, J. Fompeyrine, E. Mächler, J. W. Seo, and G. Van Tendeloo, Doubling the critical temperature of La<sub>1.9</sub>Sr<sub>0.1</sub>CuO<sub>4</sub> using epitaxial strain, *Nature (London)* **394**, 453 (1998).
- [23] O. Ivashko, M. Horio, W. Wan, N. Christensen, D. McNally, E. Paris, Y. Tseng, N. Shaik, H. Rønnow, H. Wei *et al.*, Strain-engineering Mott-insulating La<sub>2</sub>CuO<sub>4</sub>, *Nat. Commun.* **10**, 786 (2019).
- [24] S. Nakata, M. Horio, K. Koshiishi, K. Hagiwara, C. Lin, M. Suzuki, S. Ideta, K. Tanaka, D. Song, Y. Yoshida *et al.*, Nematicity in a cuprate superconductor revealed by angle-resolved photoemission spectroscopy under uniaxial strain, *npj Quantum Mater.* **6**, 86 (2021).
- [25] H.-H. Kim, S. Souliou, M. E. Barber, E. Lefrançois, M. Minola, M. Tortora, R. Heid, N. Nandi, R. A. Borzi, G. Garbarino *et al.*, Uniaxial pressure control of competing orders in a high-temperature superconductor, *Science* **362**, 1040 (2018).
- [26] M. Bluschke, A. Frano, E. Schierle, D. Putzky, F. Ghorbani, R. Ortiz, H. Suzuki, G. Christiani, G. Logvenov, E. Weschke *et al.*, Stabilization of three-dimensional charge order in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>6+x</sub> via epitaxial growth, *Nat. Commun.* **9**, 2978 (2018).
- [27] E. Wahlberg, R. Arpaia, G. Seibold, M. Rossi, R. Fumagalli, E. Trabeldo, N. B. Brookes, L. Braicovich, S. Caprara, U. Gran *et al.*, Restored strange metal phase through suppression of charge density waves in underdoped YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub>, *Science* **373**, 1506 (2021).
- [28] J. Choi, Q. Wang, S. Jöhr, N. B. Christensen, J. Kuspert, D. Bucher, D. Biscette, M. H. Fischer, M. Hucker, T. Kurosawa, N. Momono, M. Oda, O. Ivashko, M. v. Zimmermann, M. Janoschek, and J. Chang, Unveiling unequivocal charge stripe order in a prototypical cuprate superconductor, *Phys. Rev. Lett.* **128**, 207002 (2022).
- [29] N. K. Gupta, R. Sutar, R. Gong, S. H. J. Idziak, H. Hale, Y.-J. Kim, and D. G. Hawthorn, Tuning charge density wave order and structure via uniaxial stress in a stripe-ordered cuprate superconductor, *Phys. Rev. B* **108**, L121113 (2023).
- [30] J. Tranquada, B. Sternlieb, J. Axe, Y. Nakamura, and S. Uchida, Evidence for stripe correlations of spins and holes in copper oxide superconductors, *Nature (London)* **375**, 561 (1995).
- [31] F. Miletto Granozio, M. Salluzzo, U. S. di Uccio, I. Maggio-Aprile, and Ø. Fischer, Competition between  $a$ -axis and  $c$ -axis growth in superconducting RBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> thin films, *Phys. Rev. B* **61**, 756 (2000).
- [32] D. Hwang, T. Ravi, R. Ramesh, S.-W. Chan, C. Chen, L. Nazar, X. Wu, A. Inam, and T. Venkatesan, Application of a near coincidence site lattice theory to the orientations of YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> grains on (001) MgO substrates, *Appl. Phys. Lett.* **57**, 1690 (1990).

- [33] C. Eom, A. Marshall, S. Laderman, R. Jacowitz, and T. Geballe, Epitaxial and smooth films of *a*-axis YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7</sub>, *Science* **249**, 1549 (1990).
- [34] L. Luo, X. Wu, R. Dye, R. Muenchausen, S. Foltyn, Y. Coulter, C. Maggiore, and T. Inoue, *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> thin films on Si with CeO<sub>2</sub> buffer layers, *Appl. Phys. Lett.* **59**, 2043 (1991).
- [35] A. Inam, R. Ramesh, C. Rogers, B. Wilkens, K. Remschnig, D. Hart, and J. Barner, Properties of epitaxially grown *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub>-PrBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-y</sub> heterostructures, *IEEE Trans. Magn.* **27**, 1603 (1991).
- [36] S. Hontsu, N. Mukai, J. Ishii, T. Kawai, and S. Kawai, *a*-axis oriented growth of YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-y</sub> films on LaSrGaO<sub>4</sub> (100) substrates, *Appl. Phys. Lett.* **61**, 1134 (1992).
- [37] M. Mukaida and S. Miyazawa, Growth and crystallographic analysis of YBa<sub>2</sub>Cu<sub>3</sub>O<sub>x</sub> thin films on NdGaO<sub>3</sub> substrates, *Jpn. J. Appl. Phys.* **31**, 3317 (1992).
- [38] J. Hamet, B. Mercey, M. Hervieu, and B. Raveau, *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7</sub> superconducting thin film grown on MgO substrate, *Physica C (Amsterdam, Neth.)* **193**, 465 (1992).
- [39] M. Mukaida and S. Miyazawa, In-plane alignment of *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>x</sub> thin films, *Appl. Phys. Lett.* **63**, 999 (1993).
- [40] Y. Suzuki, D. Lew, A. F. Marshall, M. R. Beasley, and T. H. Geballe, Anisotropic transport properties of in-plane-aligned *a*-axis YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7</sub> films, *Phys. Rev. B* **48**, 10642(R) (1993).
- [41] W. Ito, S. Mahajan, Y. Yoshida, N. Watanabe, and T. Morishita, Superconductivity of epitaxially grown *a*-axis YBCO films on SrTiO<sub>3</sub> substrate, *J. Mater. Res.* **9**, 1625 (1994).
- [42] S. Mahajan, J. Wen, W. Ito, Y. Yoshida, N. Kubota, C.-J. Liu, and T. Morishita, Growth and superconductivity of *c*-axis in-plane aligned YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> films fabricated by the self-template method, *Appl. Phys. Lett.* **65**, 3129 (1994).
- [43] Y. K. Park, D. H. Ha, K. Park, and J.-C. Park, Growth of *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> thin films on LaSrGaO<sub>4</sub> and SrTiO<sub>3</sub> single crystal substrates by off-axis rf sputtering, *Physica C (Amsterdam, Neth.)* **235-240**, 603 (1994).
- [44] G. Y. Sung and J. D. Suh, Superconducting and structural properties of in-plane aligned *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> thin films, *Appl. Phys. Lett.* **67**, 1145 (1995).
- [45] Z. Trajanovic, I. Takeuchi, P. Warburton, C. Lobb, and T. Venkatesan, Grain growth and grain boundaries in in-plane aligned *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> films on (100) LaSrGaO<sub>4</sub>, *Phys. C (Amsterdam, Neth.)* **265**, 79 (1996).
- [46] Z. Trajanovic, I. Takeuchi, C. Lobb, T. Venkatesan, and P. Warburton, Resistivity and critical current anisotropy of untwinned *a*-axis YBCO thin films, *IEEE Trans. Appl. Supercond.* **7**, 1636 (1997).
- [47] D. Fuchs, E. Brecht, P. Schweiss, I. Loa, C. Thomsen, and R. Schneider, Growth and characterization of *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> thin films on (100) LaSrGaO<sub>4</sub> substrates, *Physica C (Amsterdam, Neth.)* **280**, 167 (1997).
- [48] R. Baghdadi, R. Arpaia, E. Stepantsov, M. Arzeo, D. Golubev, D. Montemurro, E. Andersson, T. Bauch, and F. Lombardi, Study of in-plane electrical transport anisotropy of *a*-axis oriented YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> nanodevices, *Phys. Rev. B* **95**, 184505 (2017).
- [49] T. Sueyoshi, Y. Iwanaga, T. Fujiyoshi, Y. Takai, M. Muta, M. Mukaida, A. Ichinose, and N. Ishikawa, Flux pinning by columnar defects along *a*-axis in *a*-axis oriented YBCO thin films, *IEEE Trans. Appl. Supercond.* **29**, 1 (2019).
- [50] Y. E. Suyolcu, J. Sun, B. H. Goodge, J. Park, J. Schubert, L. F. Kourkoutis, and D. G. Schlom, *a*-axis YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub>/PrBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub>/YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> trilayers with subnanometer rms roughness, *APL Mater.* **9**, 021117 (2021).
- [51] As previously shown in the literature [36,44,48], the usage of a PBCO buffer layer, on top of a (100) SLGO substrate, favors the growth of untwinned films, with the *a* axis oriented along the out-of-plane direction. The length of the PBCO *b* axis (3.91 Å in bulk form) is indeed closer to the YBCO *b* axis (3.89 Å) than to the YBCO *a* axis (3.82 Å). It is therefore energetically more favorable for the YBCO *b* axis to align along the PBCO *b* axis, i.e., on the plane of the substrate/buffer layer.
- [52] R. Arpaia, E. Andersson, E. Tralbaldo, T. Bauch, and F. Lombardi, Probing the phase diagram of cuprates with YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> thin films and nanowires, *Phys. Rev. Mater.* **2**, 024804 (2018).
- [53] E. Andersson, R. Arpaia, E. Tralbaldo, T. Bauch, and F. Lombardi, Fabrication and electrical transport characterization of high quality underdoped YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> nanowires, *Supercond. Sci. Technol.* **33**, 064002 (2020).
- [54] Z. Mori, T. Doi, and Y. Hakuraku, Oxygen diffusion in *c*-axis oriented Y<sub>1</sub>Ba<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> thin films, *J. Appl. Phys.* **110**, 033915 (2011).
- [55] R. Baghdadi, R. Arpaia, T. Bauch, and F. Lombardi, Toward YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> nanoscale structures for hybrid devices, *IEEE Trans. Appl. Supercond.* **25**, 1100104 (2015).
- [56] R. Baghdadi, R. Arpaia, S. Charpentier, D. Golubev, T. Bauch, and F. Lombardi, Fabricating nanogaps in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> for hybrid proximity-based Josephson junctions, *Phys. Rev. Appl.* **4**, 014022 (2015).
- [57] B. Wuyts, E. Osquiguil, M. Maenhoudt, S. Libbrecht, Z. X. Gao, and Y. Bruynseraede, Influence of the oxygen content on the normal-state Hall angle in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>xn</sub> films, *Phys. Rev. B* **47**, 5512(R) (1993).
- [58] J. Brötz and H. Fuess, Detwinning in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> films on vicinal SrTiO<sub>3</sub> (0 0 1) due to anisotropic strain at the interface, *Physica C (Amsterdam, Neth.)* **339**, 75 (2000).
- [59] J. M. Dekkers, G. Rijnders, S. Harkema, H. J. H. Smilde, H. Hilgenkamp, H. Rogalla, and D. H. Blank, Monocrystalline YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-x</sub> thin films on vicinal SrTiO<sub>3</sub> (001) substrates, *Appl. Phys. Lett.* **83**, 5199 (2003).
- [60] R. Arpaia, E. Andersson, A. Kalaboukhov, E. Schröder, E. Tralbaldo, R. Ciancio, G. Dražić, P. Orgiani, T. Bauch, and F. Lombardi, Untwinned YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub> thin films on MgO substrates: A platform to study strain effects on the local orders in cuprates, *Phys. Rev. Mater.* **3**, 114804 (2019).
- [61] R. Liang, D. A. Bonn, and W. N. Hardy, Evaluation of CuO<sub>2</sub> plane hole doping in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>6+x</sub> single crystals, *Phys. Rev. B* **73**, 180505(R) (2006).
- [62] J. D. Jorgensen, B. W. Veal, A. P. Paulikas, L. J. Nowicki, G. W. Crabtree, H. Claus, and W. K. Kwok, Structural properties of oxygen-deficient YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub>, *Phys. Rev. B* **41**, 1863 (1990).
- [63] C. Lowe-Ma and T. Vanderah, In search of chemical clues: Single-crystal structural studies of PrBa<sub>2</sub>Cu<sub>3</sub>O<sub>6</sub> and PrBa<sub>2</sub>Cu<sub>3</sub>O<sub>7</sub>, *Physica C (Amsterdam, Neth.)* **201**, 233 (1992).
- [64] S. Uma, T. Sarkar, K. Sethupathi, M. Seshasayee, G. Rangarajan, Chen Changkang, H. Yongle, B. M. Wanklyn, and J. W. Hodby, Structural, magnetic, and crystalline electric-field effects in single crystals of Y<sub>1-x</sub>Pr<sub>x</sub>Ba<sub>2</sub>Cu<sub>3</sub>O<sub>7-δ</sub>, *Phys. Rev. B* **53**, 6829 (1996).

- [65] J. Contour, A. Défossez, D. Ravelosona, A. Abert, and P. Ziemann, Critical thickness and stress relaxation in YBaCuO (123) strained epitaxial layers and YBaCuO based strained superlattices, *Z. Phys. B* **100**, 185 (1996).
- [66] S. Charpentier, R. Arpaia, J. Gaudet, D. Matte, R. Baghdadi, T. Löfwander, D. Golubev, P. Fournier, T. Bauch, and F. Lombardi, Hot spot formation in electron-doped PCCO nanobridges, *Phys. Rev. B* **94**, 060503(R) (2016).
- [67] L. J. van der Pauw, A method of measuring specific resistivity and Hall effect of discs of arbitrary shape, *Philips Res. Rep.* **13**, 1 (1958).
- [68] N. Barišić, M. K. Chan, Y. Li, G. Yu, X. Zhao, M. Dressel, A. Smontara, and M. Greven, Universal sheet resistance and revised phase diagram of the cuprate high-temperature superconductors, *Proc. Natl. Acad. Sci. USA* **110**, 12235 (2013).
- [69] R. Arpaia, D. Golubev, R. Baghdadi, R. Ciancio, G. Dražić, P. Orgiani, D. Montemurro, T. Bauch, and F. Lombardi, Transport properties of ultrathin YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7- $\delta$</sub>  nanowires: A route to single-photon detection, *Phys. Rev. B* **96**, 064525 (2017).
- [70] Z. Sefrioui, D. Arias, M. Varela, J. E. Villegas, M. A. Lopez de la Torre, C. León, G. D. Loos, and J. Santamaria, Crossover from a three-dimensional to purely two-dimensional vortex-glass transition in deoxygenated YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7- $\delta$</sub>  thin films, *Phys. Rev. B* **60**, 15423 (1999).
- [71] T. A. Friedmann, M. W. Rabin, J. Giapintzakis, J. P. Rice, and D. M. Ginsberg, Direct measurement of the anisotropy of the resistivity in the *a-b* plane of twin-free, single-crystal, superconducting YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7- $\delta$</sub> , *Phys. Rev. B* **42**, 6217 (1990).
- [72] K. Takenaka, K. Mizuhashi, H. Takagi, and S. Uchida, Inter-plane charge transport in YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7- $\gamma$</sub> : Spin-gap effect on in-plane and out-of-plane resistivity, *Phys. Rev. B* **50**, 6534 (1994).
- [73] V. Zverev and D. Shovkun, Anisotropy of normal resistivity in oxygen-deficient YBa<sub>2</sub>Cu<sub>3</sub>O<sub>7- $x$</sub>  single crystals, *J. Exp. Theor. Phys.* **72**, 73 (2000).
- [74] J. M. Tranquada, G. D. Gu, M. Hücker, Q. Jie, H.-J. Kang, R. Klingeler, Q. Li, N. Tristan, J. S. Wen, G. Y. Xu, Z. J. Xu, J. Zhou, and M. v. Zimmermann, Evidence for unusual superconducting correlations coexisting with stripe order in La<sub>1.875</sub>Ba<sub>0.125</sub>CuO<sub>4</sub>, *Phys. Rev. B* **78**, 174529 (2008).
- [75] A. S. Disa, T. F. Nova, and A. Cavalleri, Engineering crystal structures with light, *Nat. Phys.* **17**, 1087 (2021).
- [76] M. Buzzi, M. Först, R. Mankowsky, and A. Cavalleri, Probing dynamics in quantum materials with femtosecond x-rays, *Nat. Rev. Mater.* **3**, 299 (2018).
- [77] Y. Makhlin, G. Schön, and A. Shnirman, Quantum-state engineering with Josephson-junction devices, *Rev. Mod. Phys.* **73**, 357 (2001).
- [78] A. Blais, A. L. Grimsmo, S. M. Girvin, and A. Wallraff, Circuit quantum electrodynamics, *Rev. Mod. Phys.* **93**, 025005 (2021).